

	FICHE TECHNIQUE PRODUIT	Date d'émission 31/03/2026 Fin de validité 30/09/2026
--	--------------------------------	--

Site de production	SISAG - ATTINGUIE	Granulat	0/4 Sable
Nature pétrographique	Granulat	Elaboration	Naturel


Partie normative
Valeurs spécifiées sur lesquelles le fournisseur s'engage

Classe granulaire **0** **4** Norme

	0.063	0.08	0.2	0.315	0.5	0.63	1	D/2 2	2.5	3.15	D 4	5	6.3	f (%)	W (%)
Vss + u	16		28				62	84	90	96	99	100			
Vss	16		28				62	84	90	96	99	100			
Vsi	9		15				38	58	67	80	92	100	100		
Vsi - u	9		15				38	58	67	80	92	100	100		
sf Max															

Partie informative
Résultat des essais de fabrication : du 30/11/2025 au 31/03/2026 Résultat des autres essais : du 30/11/2025 au 31/03/2026

	0.063	0.08	0.2	0.315	0.5	0.63	1	D/2 2	2.5	3.15	D 4	5	6.3	f (%)	W (%)
Nbr. val	38	38	38	38	38	38	38	38	38	38	38	38	38	38	38
Maxi	13.4	15.6	24.1	30.4	38.0	42.4	53.5	76.3	85.8	94.7	99.0	100.0	100.0	13.4	4.0
XF + 1.25 sf	12.7	14.8	23.6	29.5	36.9	41.3	52.4	75.0	83.8	93.3	98.7	100.0	100.0	12.7	2.7
XF	11.8	13.8	22.2	27.9	35.1	39.3	50.2	72.8	81.6	91.6	98.1	100.0	100.0	11.8	1.7
XF - 1.25 sf	10.9	12.8	20.8	26.3	33.3	37.3	48.0	70.6	79.4	89.9	97.5	100.0	100.0	10.9	0.8
Mini	9.7	11.6	19.3	25.0	31.7	35.4	45.8	67.9	77.3	88.2	96.6	100.0	100.0	9.7	0.8
sf	0.70	0.78	1.09	1.26	1.45	1.58	1.76	1.79	1.75	1.36	0.48	0.00	0.00	0.70	0.76

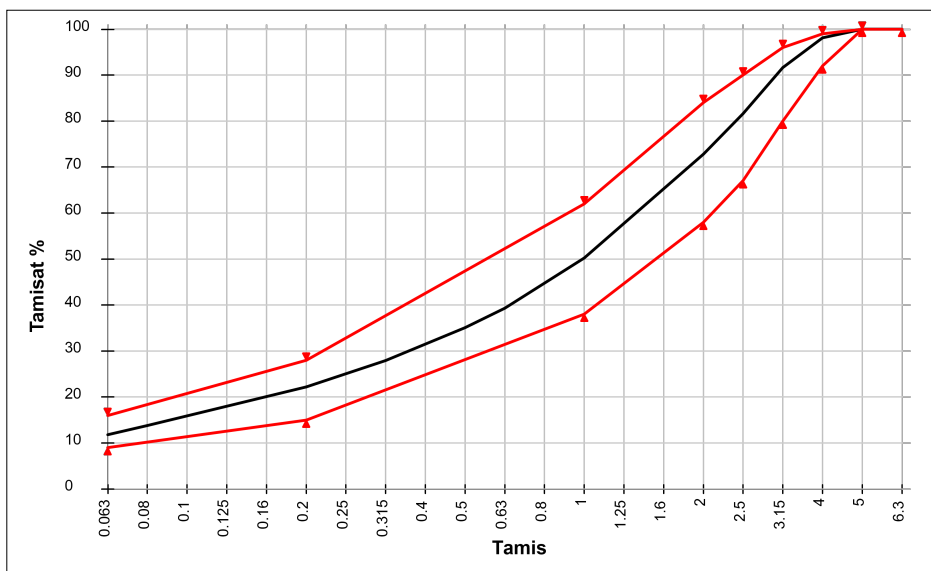

Essai(s) complémentaire(s)	
Pa	EXTERNE
Pb	EXTERNE
VBS	EXTERNE

FTP (Fiche Technique Produit) NF P18-545

KOUADIO MARCEL ARNAUD
CONTROLEUR QUALITE

